



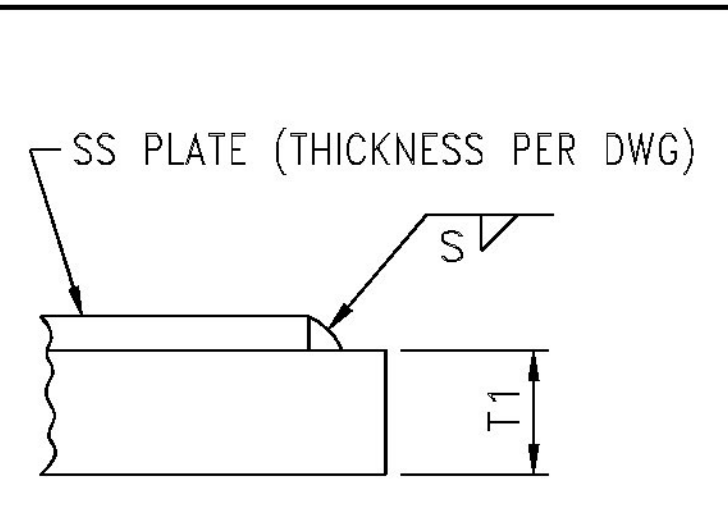
Production Joint Welding Procedure Specification (D1.6-07)

Procedure No: A-GTF-01 Date Issued: 1-9-04 Revision No: 02 Rev. Date: 9/20/12

Contractor (Fabricator) D.S. Brown Company Prepared by: Brad Streeter, Quality Assurance Manager

1. Non-Fracture Critical Fracture Critical WPS Expiration Date: _____
2. Qualified in accordance with: AWS D1.5-AWS D1.6-07
 Referenced PQR No(s). PQR-GTAW-01-(10)NY , _____ , _____
 Referenced FWST No(s). _____ , _____ , _____
3. Material specification(s) ASTM A709 Gr. 36, 50, 50W, 304SS, 316SS For DOT Approval
4. Material Thickness (es) Unlimited
5. Welding process GTAW
6. Manual , machine , or semiautomatic
7. Position(s) of welding 1F, 2F
8. Filler metal specification AWS A5.9
9. Filler metal class and brand name ER309L
10. Flux class & brand N/A , Type N/A
11. Shielding gas 100% Argon Flow rate 20 CFH
12. Single pass Or multiple pass
13. Single arc Or multiple arc
14. Welding Current DCEN
15. Polarity Straight
16. Welding progression stringers
17. Root treatment Clean to bright sound metal or per AWS D1.5 (3.2.1 & 3.11)
18. Postheat treatment N/A
19. Calculated Heat Input (KJ/In) Min 10.9 KJ Max 20.4 KJ
20. Electrode extension (electrical stickout) N/A

Vermont Agency of Transportation
RECEIVED
Monday, 12/01/17 10:00 AM
 CK'D BY CLB OK'D BY CWC
December 1, 2017
 RESUBMIT NO Approved
 BY C. CARLSON DATE 12/08/17

Weld size (In)	Pass No(s)	Electrode Size (In)	Welding Process Variables		Travel Speed (IPM)	Joint Detail (Fillet Weld) Show all dimensions, weld sizes, passes, and AWS symbols
			AMPS/WFS*	VOLTS		
20 ga.	1	1/8"	170-200	19-21	12.6-15.4	
16 ga.	1	1/8"	170-200	19-21	12.6-15.4	
14 ga.	1	1/8"	170-200	19-21	12.6-15.4	
12 ga.	1	1/8"	170-200	19-21	12.6-15.4	
11 ga.	1	1/8"	170-200	19-21	12.6-15.4	
10 ga.	1	1/8"	170-200	19-21	12.6-15.4	
8 ga.	1	1/8"	170-200	19-21	12.6-15.4	
3/16"	1	1/8"	170-200	19-21	12.6-15.4	

* Wire feed speed may be used along with amperage (include chart)

Prepared By: [Signature] DSB QA Manager

Project: _____

DSB Job: 53146-1114 VT

Base Metal Thickness range	Minimum Preheat (°F)	Max Preheat & Interpass (°F)
≤ 3/4"	50°F	450°F
>3/4" to ≤1.5"	70°F	450°F
>1.5" to ≤2.5"	150°F	450°F
>2.5"	225°F	450°F

Note: When this procedure is used for A709Gr50W materials, it shall be limited to 5/16" single pass or material be coated.