

Highway Safety Corporation

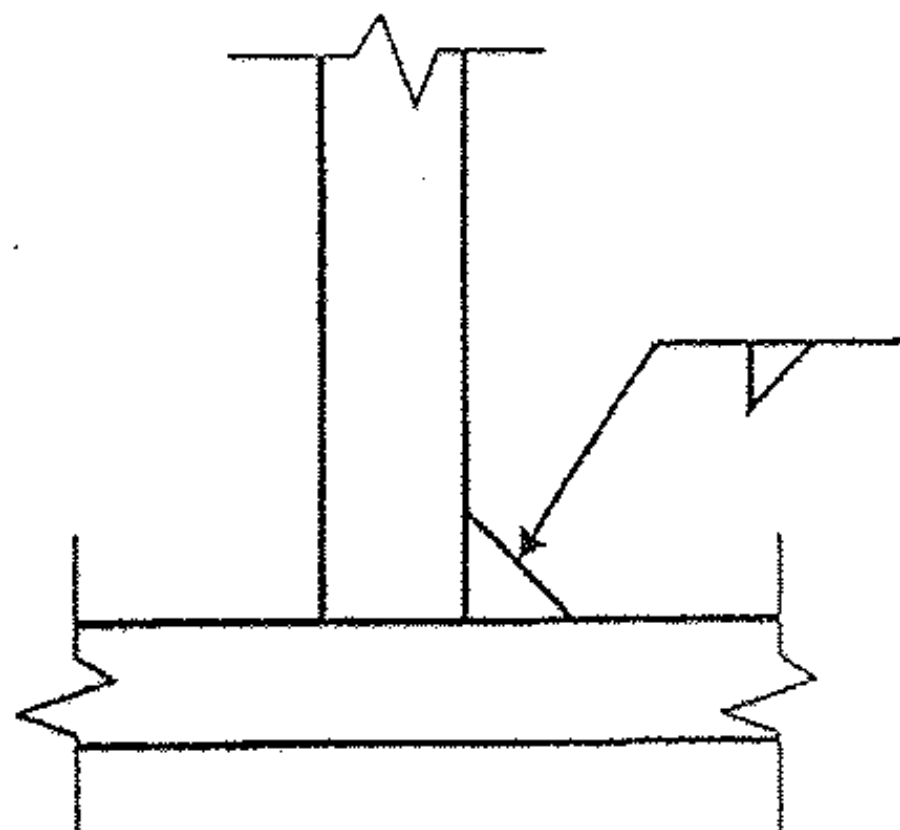
Glastonbury, CT

Welding Procedure Specification

Material specification ASTM A709 gr 36/gr 50, ASTM A572 gr.36/gr.50, ASTM A36, A500 gr.B
 Welding process Gas Metal Arc Welding (GMAW) Spray Transfer
 Manual, semi-automatic, or automatic Semi-Automatic
 Position of welding Flat (1F) or Horizontal (2F)
 Filler metal specification AWS A5.18
 Filler metal classification ER70S-6
 Electrode and manufacturer Lincoln Electric Lincoln Weld L-56
 Flux and manufacturer N/A
 Shielding gas 86% Argon / 14% CO2 Flow rate 35-45 CFM
 Single or multiple pass Single
 Single or multiple arc Single
 Welding current DCEP
 Polarity Reverse - electrode positive
 Welding progression Stringers
 Root treatment clean base metal
 Preheat and interpass temperature base metal up to 3/4" (50°F)
 Postheat treatment None
 Electrode extension 3/4" ± 1/4"

VTrans
 Received
 CK'D _____ OK'D BY [Signature]
 NOV 14 2011
 Resubmit _____ APPROVED ✓
 BY _____ DATE 11/15/11


WELDING PROCEDURE

Weld size	Pass no.	Electrode size	Welding parameters		Travel speed	Joint detail
			Amperes	Volts		
1/8	1	.063"	300 A ± 30	29 V ± 2	15 ipm ± 2	TYPICAL FILLET WELDS (5/16" MAX) 
3/16	1	.063"	300 A ± 30	29 V ± 2	15 ipm ± 2	
1/4	1	.063"	300 A ± 30	29 V ± 2	15 ipm ± 2	
5/16	1	.063"	300 A ± 30	29 V ± 2	15 ipm ± 2	

This procedure may vary due to fabrication sequence, fit-up, pass size, etc. within the limitation of variables given in section 5 of latest edition AWS D1.1 / D1.5

WPS no. W-1PFILLET
 Revision no. 1
 Supporting PQR no. Pre-Qualified
 Project Name BETHEL, VT

Fabricator Highway Safety Corporation
 Prepared by Robert Light
 Date 06/22/2011
 Project Number BLAF 0241 (30)

 Paul A Radice
 CWI 98070224
 QC1 EXP. 7/1/2013