

LB FOSTER CO Precise Structural Products

Welding Procedure Specification

STRUCTURAL STEEL **70**

Page 1 of 2

VT AOT 02

Material Spec. ASTM A709 G36, G50 & G50W AASHTO M270 G36, G50 & G50W

Welding Process(es) SAW Vermont Agency of Transportation

Position of Welding 1F & 2F

Manual Machine Semi-Automatic Automatic

Filler Metal Specification AWS A5.23 **RECEIVED**

Filler Metal Classification F7A2-ENi1K-Ni1-H8 CK'D BY WDL OK'D BY JWC

Flux LINCOLN 860 **11:43 am, Jul 11, 2011**

Shielding Gas N/A Gas Flow Rate N/A RESUBMIT APPROVED

Single or Multiple Pass BOTH BY CWC, Proj. Mgr. DATE 07/19/11

Single or Multiple Arc SINGLE

Welding Current REVERSE

Polarity: AC DCEP DCEN Pulsed

Welding Progression Up Down

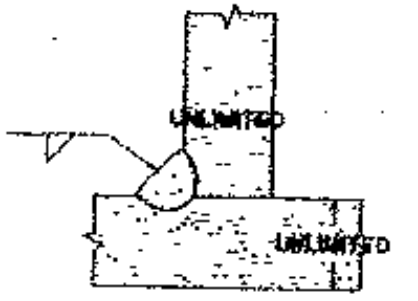
Root Treatment CLEAN AS TO REMOVE CONTAMINANTS

Preheat Temperature *** SEE PAGE 2 Interpass Temperature *** SEE PAGE 2

Postheat Treatment N/A

Heat Input Min 48.55 KILOJOULES/IN Max 76.29 KILOJOULES/IN

WELDING PROCEDURE

Pass No.	Electrode Size	Amperes	Volts	Travel Speed	Other	Joint Detail
All	5/64	330-350	33-35	10-11		

This procedure may vary due to fabrication sequence, fit-up, pass size, etc., within the limitation of variables given in Section 5.

Procedure No. 001 - FILLET WELD Contractor _____

Revision No. _____ Authorized By WALTER J. BORKOWSKI Date 7/11/2011