

**DSBROWN Production Joint Welding Procedure Specification (D1.5-02)**


Procedure No: A-FPB-01 Date Issued: 8-14-06 Revision No: 0 Rev. Date: \_\_\_\_\_

Contractor (Fabricator) D.S. Brown Company Prepared by: James R. Connor, Quality Assurance Manager

1. Non-Fracture Critical  Fracture Critical  WPS Expiration Date: \_\_\_\_\_
2. Qualified in accordance with: AWS D1.5-2002 (S.12.1)  
 Referenced PQR No(s): PQR-FCAW-01-03  
 Referenced FWST No(s): PQR-FCAW-FWST-01(03), PQR-FCAW-FWST-01A(03)
3. Material specification(s) ASTM A709 Gr. 36, 50, 50W, A500b to CF1018, CF1040, A615 (Rebar) For DOT Approval
4. Material Thickness (es) Unlimited
5. Welding process FCAW
6. Manual , machine , or semiautomatic
7. Position(s) of welding 1G,2G,1F,2F
8. Filler metal specification AWS A5.20
9. Filler metal class and brand name E71T-1 Lincoln Outershield Elite
10. Flux class & brand N/A, Type N/A
11. Shielding gas 100% CO2 Flow rate 45 CFH
12. Single pass  Or multiple pass
13. Single arc  Or multiple arc
14. Welding Current DCEP
15. Polarity Reverse
16. Welding progression stringers
17. Root treatment Clean to bright sound metal or per AWS D1.5 (3.2.1 & 3.11)
18. Postheat treatment N/A
19. Calculated Heat Input (KJ/in) Min 31.20 KJ/in Max 50.72 KJ/in
20. Electrode extension (electrical stickout) 3/4"

TRAINS RECEIVED  
 JUN 21 2007  
 APPROVED BY: \_\_\_\_\_  
 DATE: 7-23-07

Weld size (in)	Pass No(s)	Electrode Size (in)	Welding Process Variables		Travel Speed (IPM)
			AMPS/WFS*	VOLTS	
**1/4"	1	1/16"	260-310	26-30	11-13
5/16"	1	1/16"	260-310	26-30	11-13
3/8"	2-3	1/16"	260-310	26-30	11-13
7/16"	3-5	1/16"	260-310	26-30	11-13
1/2"	4-6	1/16"	260-310	26-30	11-13
5/8"	5-7	1/16"	260-310	26-30	11-13
3/4"	6-8	1/16"	260-310	26-30	11-13

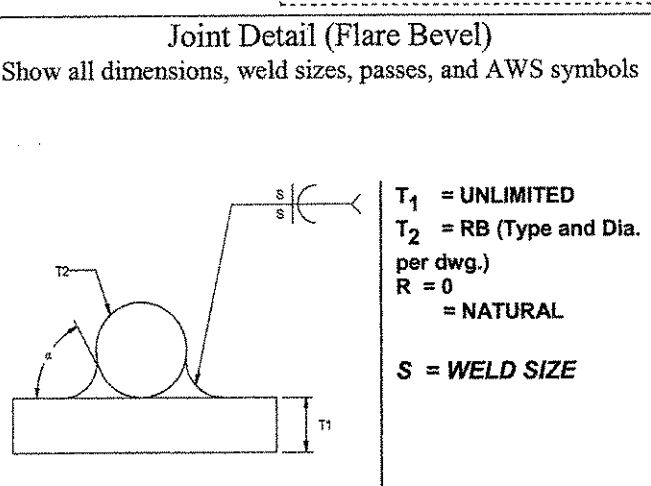

\* Wire feed speed may be used along with amperage (include chart)

Prepared By: <u>James R. Connor</u> DSB QA Manager	Preheat and Interpass Temperature Chart		
	Base Metal Thickness range	Minimum Preheat (°F)	Max Preheat & Interpass (°F)
Project: <u>Route No. TH 7/11, CL3</u>	≤ 3/4"	50°F	450°F
DSB Job: <u>20388-1206</u>	>3/4" to ≤1.5"	70°F	450°F
	>1.5" to ≤2.5"	150°F	450°F
	>2.5"	225°F	450°F

Note: When this procedure is used for A709Gr50W materials, it shall be limited to 5/16" single pass or material be coated.

078-BRWTF